

THEORETICAL STUDY OF THE CARBONE(IV) DOPED ANATASE SURFACES OF TiO₂

E. Esra KASAPBASI

Department of the Food Engineering, Faculty of Engineering Istanbul Aydin Istanbul/ Turkey

E-mail: eminekasapbasi@aydin.edu.tr

Abstract: *In this study photocatalytic activity of TiO₂ doped with C(IV) has been investigated using DFT (Density Functional Theory) calculations. This calculations are utilized to illuminate and classify the effect of C(IV)-doping on the electronic and structural properties of TiO₂, neutral, stoichiometric clusters Ti₇O₁₈H₈ and Ti₂₅O₅₅H₁₀ cut from the anatase bulk structure and three new models for the C(IV)-doped TiO₂ were developed. The DFT calculations were carried out by the hybrid B3LYP functional, by using double-zeta, LanL2DZ basis set. The DFT calculations indicated that C(IV)-doping of TiO₂ enhances the visible-light photocatalytic activity.*

Keywords: TiO₂, anatase, C-doped, DFT

Introduction

In many studies properties of titanium have been investigated and proved to be the most effective and suitable photocatalyst for the degradation of environment pollutants, selfcleaning and solar cell applications [1]. In [2-4] TiO₂ has been proved to be most suitable photocatalyst for application in photocatalysis to degrade refractory organic compounds in water or air. For heterogeneous photocatalysis anatase form of TiO₂ has also been proved to very effective compared to various semiconductor photocatalysts (WO₃, ZnO, ZnS, Fe₂O₃, CdS and SrTiO₃) [5,6]. Although details on the microscopic mechanisms concerning the excited states involved in the process are still a matter of debate [7], under UV irradiation properties of TiO₂ are known for many years [8-11]. It is a critical issue to reduce the band gap of anatase TiO₂ for improving its

photocatalytic applications. Therefore in different studies anatase TiO₂ doped either with nonmetal elements (C, N, F or S) or metal elements (Se, Fe, V etc.) elements aiming to reduce the band gap and improve photocatalytic activity under visible light [12–18].

In this study using DFT (Density Functional Theory) electronic structure, optical and photocatalytic properties of C doped TiO₂ with different substitute sites are analyzed in order to illuminate activity of the photocatalyst in regards to C(IV) the dopant. Using DFT undoped and C(IV) doped titania cluster models are calculated to elucidate the structural and electronic properties. This study may provide new insights of photoactivity enhancement by C(IV)-doping into the lattice of TiO₂.

THEORETICAL STUDY OF THE CARBONE(IV) DOPED ANATASE SURFACES OF TiO₂

E. Esra KASAPBASI

Method

The DFT techniques are used to understand the effect of C(IV) dopant on the structural and electronic properties of C(IV)-doped TiO₂. Since it is well-known, the Degussa P25 powder has include the anatase phase more than the others. The surface of anatase particles predominantly consists of the (101), (100) and (001) lattice planes. Since (001) surface has the highest photocatalytic activity [19], hence it has been modelled to determine the location and the bonding status of the dopant ion, TiO₂ molecules. This model is cut from the anatase bulk structure. The unitcell for anatase has a tetragonal structure with the bulk lattice constants $a = b = 3.78 \text{ \AA}$ and $c = 9.51 \text{ \AA}$ [20]. In the modelled clusters, the unsaturated oxygen atoms were completed with hydrogen's and titanium atoms with OH groups. Using quantum mechanical techniques three new models for the C(IV) doped photocatalyst were developed. The studied three cluster models were Ti₉O₂₁H₆ (Model A) Ti₁₅O₃₇H₁₄ (Model B) Ti₂₅O₅₅H₁₀ (Model C). In these models, replacing one Ti atom whose coordination number was equal to 4 with one C(IV) is performed to constructed the structure of the C(IV) doped TiO₂. In the developed cluster models, all the distances were fixed at the bulk values. All the calculations were carried out using the DFT method [21-22] with in the GAUSSIAN 09 package [23] due to the fact that it takes electron correlation in to account. The DFT calculations were performed by the hybrid B3LYP [24] functional. The double-zeta (LanL2DZ) [25] basis set was used. The cluster geometry was frozen throughout all the

calculations, but the dopant, terminal hydrogens and the OH groups were relaxed. The geometric parameters, the band edges, the band gap energies and Mulliken charge distributions of the atoms on the undoped, C(IV) doped photocatalyst surfaces were calculated. By changing the location of C(IV) ion with different Ti atoms in the surface for each model A, B and C many models are generated to choose the best photocatalytic activity structure.

Result And Discussion

The Figure 1-3 represents the structures obtained for the C(IV)-doped TiO₂ cluster models with minimum energy structure. Electronic structure calculations of the models indicate structures with deviations, which are not as symmetrical as that of the undoped part of TiO₂ model. The results indicate that the size and electronegativity difference between the C (IV) cation and Ti (IV) induce structural changes. The calculated results show that the C(11)–O(7) bond length, 1.46 Å was found to be shorter than Ti(2)–O(3) bond length 1.93 Å for Model A, which is consistent with the different electronegativity's and ionic radius of C(IV) (30.0 pm) and Ti(IV) (74.5 pm). The results of shortening of this bond the O(12)–C(11)–O(7) angle from its original value reduced from 116.1⁰ to 92.4⁰ that in the undoped part while C(11)–O(10) bond lengthens increased from 1.930 Å to 2.48 Å. As a result C (IV) doping causes defacement in the TiO₂ lattice. We also experienced same type of changes in Model B and Model C. Depending on the position of the doped C(IV) these bond distances and angles also change. Values that are given in those figures 1-3 belong to the minimum energy structures for Model B and Model C.

THEORETICAL STUDY OF THE CARBONE(IV) DOPED ANATASE SURFACES OF
 TiO₂
 E. Esra KASAPBASI

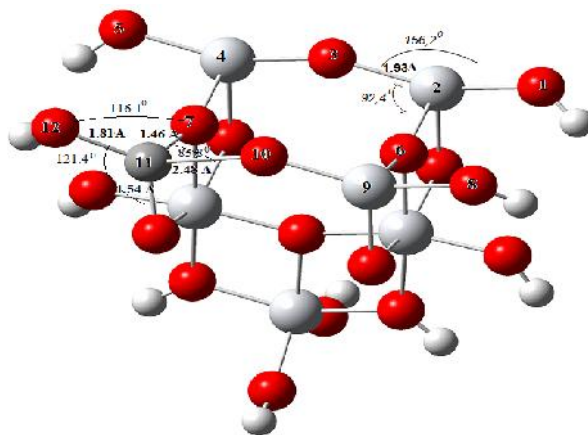


Figure 1: Optimized structure of the C(IV)-doped TiO₂ Model A cluster with some distances and angles

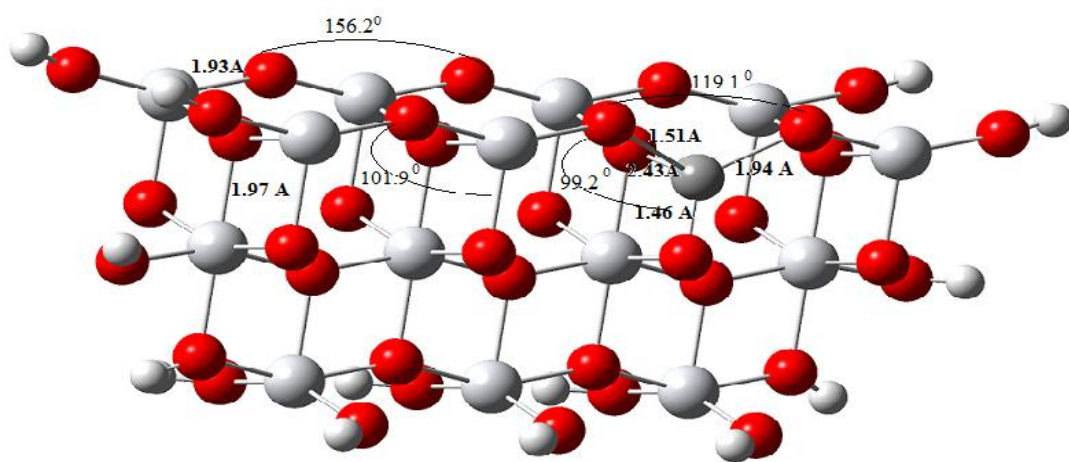


Figure 2: Optimized structure of the C(IV)-doped TiO₂ Model B cluster with some distances and angles

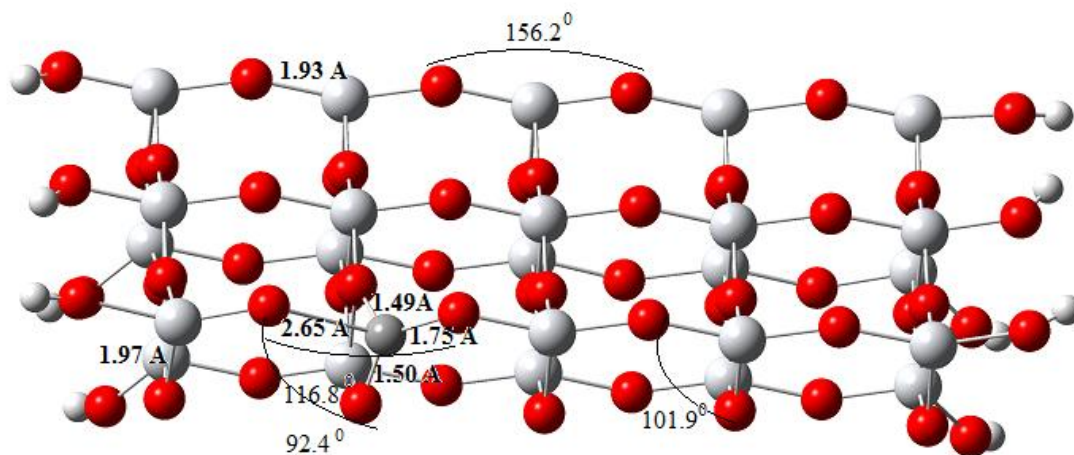


Figure 3: Optimized structure of the C(IV)-doped TiO₂ Model C cluster with some distances and angles

THEORETICAL STUDY OF THE CARBONE(IV) DOPED ANATASE SURFACES OF TiO₂

E. Esra KASAPBASI

The different electronegativity of the C (IV) dopant causes a redistribution of local charges of the surface atoms, which may enhance the photocatalytic activity. Mulliken charge distributions of the surface atoms of Model A showed in Figure 4. reflect the behavior of the dopant in the doped cluster models. In the doped model, the positive charge on surface Ti cations increases to 1.41-1.46 while the dopant C (IV) carries less positive charge 0.9 than the lattice Ti s. The negative charge on Os was found to be increased from 0.9 to 1.4 correspondingly due to C (IV)-doping. The reason may be explained by the fact that the dopant C(IV) is more electronegative.

While four- and fivefold-coordinated titanium atoms shows Lewis acidic characteristics, the two- and threefold-coordinated oxygen atoms behaves as Lewis base sites for the exposed atoms on the (001) surface of Model B and Model C.

A schematic diagram of the electronic energy levels for the undoped and C(IV)-doped anatase models obtained from electronic structure calculations are presented in Figure 5. This figures explains the highest occupied HOMO and the lowest unoccupied molecular orbitals LUMO energies for the studied structures. The valence band (VB) and conduction band (CB) those bands related to HOMO LUMO energies. The experimental band-gap energy of the undoped TiO₂ (3.2 eV) was adopted as the benchmark to correct the calculated values of the anatase (001) surface. The calculated band-gap was corrected using an operator that displaces the empty and occupied bands relative to each other by a rigid shift of 0.41 eV for Model C, 0.36 eV for Model B and 0.03 eV for Model A to bring the minimum band-gap in line with experiment for the band-gap of anatase. These intermediate energy levels offer additional steps for the absorption of low energy photons through the excitation of VB electrons to these intermediate energy levels, from where they can be excited again to the CB.

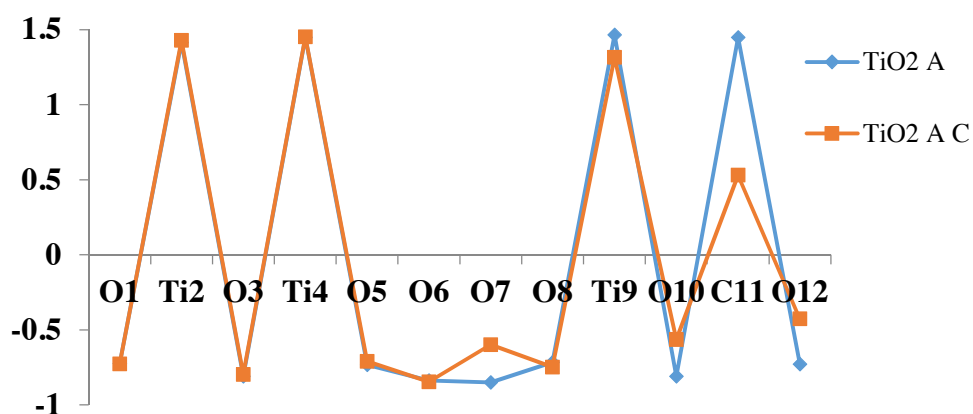


Figure 4: The surface atoms Mulliken charge for undoped and C(IV)-doped TiO₂ clusters

THEORETICAL STUDY OF THE CARBONE(IV) DOPED ANATASE SURFACES OF
TiO₂
E. Esra KASAPBASI

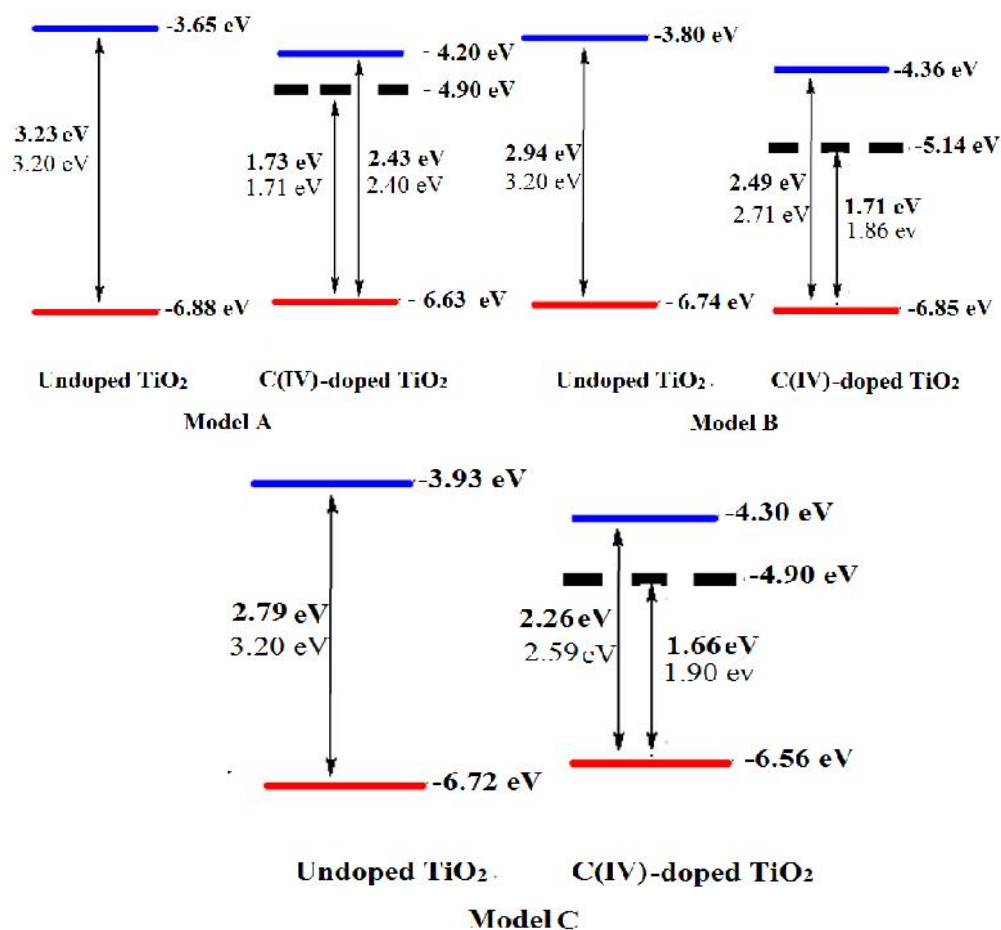


Figure 5. The valence band (VB) and conduction band (CB) edges of of C-doped TiO₂ molecules

Table 1 Energies of C-doped TiO₂ molecules in ev

	Energy	HOMO-1	HOMO	LUMO	LUMO+1	LUMO-(HOMO-1)	LUMO-HOMO	(LUMO+1)-HOMO
TiO ₂ A	-50158.50	-7.17	-6.89	-3.65	-3.56	3.52	3.23	3.33
TiO ₂ A C	-49602.01	-6.94	-6.63	-4.90	-4.20	2.04	1.73	2.44
TiO ₂ B	-99758.11	-6.86	-6.74	-4.01	-3.80	2.85	2.73	2.94
TiO ₂ B C1	-99200.41	-5.95	-5.87	-4.77	-4.39	1.18	1.10	1.48
TiO ₂ B C2	-99201.48	-6.99	-6.95	-5.29	-4.46	1.70	1.66	2.49
TiO ₂ B C3	-99201.55	-7.02	-6.85	-5.14	-4.36	1.89	1.71	2.49
TiO ₂ C	-152403.20	-6.90	-6.72	-3.93	-3.84	2.97	2.79	2.88
TiO ₂ C C1	-151845.70	-6.48	-6.44	-5.00	-4.11	1.49	1.44	2.33
TiO ₂ C C2	-151847.69	-6.74	-6.56	-4.90	-4.30	1.85	1.66	2.26
TiO ₂ C C3	-151846.81	-6.85	-6.57	-4.87	-4.15	1.97	1.69	2.42
TiO ₂ C C6	-151844.87	-6.35	-6.06	-4.83	-4.51	1.52	1.23	1.55

THEORETICAL STUDY OF THE CARBONE(IV) DOPED ANATASE SURFACES OF TiO₂

E. Esra KASAPBASI

Conclusion

TiO₂ was doped with C (IV) ions to obtain a visible light active photocatalyst with high photocatalytic activity. Characterization techniques showed that the C (IV) is in O–C bond is shorter than Ti–O bond in the crystal lattice. Beside this C (IV) charge is less positive than Ti (IV). The absorption threshold of the C (IV)-doped photocatalyst shifted to the visible region of the spectrum. We can understand from the result of DFT calculations that HOMO LUMO band gap has not been effected from that C (IV)-doping of TiO₂. However due to C 3p orbitals in the band gap, C (IV)-doping of TiO₂ resulted in an additional electronic states. Also these localized mid-gap levels resulted in the visible light photocatalytic activity of the C (IV)-doped TiO₂. Changes in the photocatalytic activity of doped TiO₂ are due to change in binding position of the C atoms.

Acknowledgments

In our DFT calculations have used the computing resources of the High Performance and Grid Computing Center at NCSU (<http://www.ncsu.edu/itd/hpc/main.php>).

References

[1] A. Fujishima and K. Honda. *Nature*, 238, 37 (1972). doi:10.1038/238037a0. PMID:12635268.
[2] A. Mills, S. Le Hunte, An overview of semiconductor photocatalysis, *J. Photochem. Photobiol. A* 108 (1997) 1–35.
[3] D. Bahnemann, J. Cunningham, M.A. Fox, E. Pelizzetti, P. Pichat, N. Serpone, in: G.R. Helz, R.G. Zepp, D.G. Crosby (Eds.), *Aquatic and Surface Photochemistry*, Lewis, Boca Raton, FL, 1994, p. 261.
[4] P. Pichat, in: G. Ertl, H. Knozinger, J. Weitkamp (Eds.), *Handbook of Heterogeneous Photo-Catalysis*, vol. 4, VCH, Weinheim, 1997, p. 2111.
[5] D.F. Ollis, E. Pelizzetti, N. Serpone, Destruction of water contaminants. *Environ. Sci. Technol.* 25 (1991) 1523–1529.

[6] D.W. Bahnemann, D. Bockelmann, R. Goslich, Mechanistic studies of water detoxification in illuminated TiO₂ suspensions, *Sol. Energy Mater.* 24 (1991) 564–583.
[7] C. Sousa, S. Tosoni, F. Illas *Chem. Rev.*, 113 (2013), p. 4456
[8] K. Hashimoto, H. Irie, A. Fujishima *Jpn. J. Appl. Phys.*, 44 (2005), p. 8269
[9] A. Fujishima, X. Zhang, D.A. Tryk *Surf. Sci. Rep.*, 63 (2008), p. 515
[10] X. Chen, S.S. Mao *Chem. Rev.*, 107 (2007), p. 2891
[11] M.A. Henderson *Surf. Sci. Rep.*, 66 (2011), p. 185
[12] J. Tang, Z. Zou, and J. Ye. *Catal. Lett.* 92, 53 (2004). doi:10.1023/B:CATL.0000011086.20412.aa.
[13] X. Xiang, D. Chang, Y. Jiang, C.M. Liu, and X.T. Zu. *Can. J. Phys.* 90, 39 (2012). doi:10.1139/p11-136.
[14] B. Chi, L. Zhao, and T. Jin. *J. Phys. Chem. C*, 111, 6189 (2007). doi:10.1021/jp067490n.
[15] S.X. Zhang, S.Y. Wu, P. Xu, and L.L. Liu. *Can. J. Phys.* 88(1), 49 (2010). doi:10.1139/P09-110.
[16] L.C. Jia, C.C. Wu, Y.Y. Li, S. Han, Z. Li, B. Chi, J. Pu, and L. Jian *Appl. Phys. Lett.* 98, 211903 (2011). doi:10.1063/1.3593147.
[17] L.C. Jia, C.C. Wu, S. Han, N. Yao, Y. Li, Z. Li, B. Chi, J. Pu, and L. Jian. *J. Alloys Compd.* 509, 6067 (2011). doi:10.1016/j.jallcom.2011.03.012.
[18] Yelda Y. Gurkan 1, Esra Kasapbasi, Zekiye Cinar *Chemical Engineering Journal* 214 (2013) 34–44
[19] T. Homann, T. Bredow, K. Jug, Adsorption of small molecules on the anatase (100) surface, *Surf. Sci.* 555 (2004) 135–144.
[20] T. Sekiya, M. Igarashi, S. Kurita, S. Tokekawa, M. Fujisawa, Structure dependence of reflection spectra of TiO₂ single crystals, *J. Elec. Spec. Rel. Phen.* 92 (1998) 247–250.
[21] Stephens, P. J.; Devlin, F. J.; Chabalowski, C. F.; Frisch, M. J. *J. Phys. Chem.* 1994, 98, 11623.
[22] Stephens, P. J.; Devlin, F. J.; Ashvar, C. S.; Bak, K. L.; Taylor, P. R.; Frisch, M. J. *ACS Symp. Ser.* 1996, 629, 105.
[23] M.J. Frisch, G.W. Trucks, H.B. Schlegel, G.E. Scuseria, M.A. Robb, J.R. Cheeseman, J.A. Montgomery Jr., T. Vreven, K.N. Kudin, J.C. Burant, J.M. Millam, S.S. Iyengar, J. Tomasi, V. Barone, B. Mennucci, M. Cossi, G. Scalmani, N. Rega, G.A. Petersson, H. Nakatsuji, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai,

THEORETICAL STUDY OF THE CARBONE(IV) DOPED ANATASE SURFACES OF
TiO₂

E. Esra KASAPBASI

M. Klene, X. Li, J.E. Knox, H.P. Hratchian, J.B. Cross, C. Adamo, J. Jaramillo, R. Gomperts, R.E. Stratmann, O. Yazyev, A.J. Austin, R. Cammi, C. Pomelli, J.W. Ochterski, P.Y. Ayala, K. Morokuma, G.A. Voth, P. Salvador, J.J. Dannenberg, V.G. Zakrzewski, S. Dapprich, A.D. Daniels, M.C. Strain, O. Farkas, D.K. Malick, A.D. Rabuck, K. Raghavachari, J.B. Foresman, J.V. Ortiz, Q. Cui, A.G. Baboul, S. Clifford, J. Cioslowski, B.B. Stefanov, G. Liu, A. Liashenko, P. Piskorz, I. Komaromi, R.L. Martin, D.J. Fox, T. Keith, M.A. Al-Laham, C.Y. Peng, A. Nanayakkara, M. Challacombe, P.M.W. Gill, B. Johnson, W. Chen, M.W. Wong, C. Gonzalez, J.A.

[24] Becke, A. D. J. Chem. Phys. 1993, 98, 5648.

[25] P. J. Hay and W. R. Wadt, "Ab initio effective core potentials for molecular calculations - potentials for the transition-metal atoms Sc to Hg," J. Chem. Phys., 82 (1985) 270-83.

THEORETICAL STUDY OF THE CARBONE(IV) DOPED ANATASE SURFACES OF
TiO₂
E. Esra KASAPBASI